arXiv:cond-mat/0008270v1 [cond-mat.supr-con] 18 Aug 2000

An Empirical Pair-breaking Picture for the Non-linear Meissner Effect in d-wave Superconductors

J.R. Cooper
IRC in Superconductivity and Physics Department,
University of Cambridge, Madingley Road, Cambridge, CB3 OHE, U.K.

(February 1, 2008)

A empirical model is proposed for the observed variation of the London penetration depth of cuprate superconductors with applied magnetic field H below the lower critical field H_{c1}. It is suggested that the Doppler shift of the quasi-particle energies near the d-wave nodes could cause pair-breaking and that this could be responsible for the non-linear Meissner effect (NLME) investigated in recent experiments. This picture gives a somewhat better description of the observed temperature and field dependencies than the original theory proposed by Yip and Sauls. A calculation based on weak-coupling BCS theory suggests that when there is a finite supercurrent, the state for which pairs are broken in a small angular range around the nodes can have a lower free energy than the $d_{x^2-y^2}$ state.

I. INTRODUCTION

There is now a large body of experimental evidence [1–3] showing that the order parameter of all cuprate superconductors has unconventional $d_{x^2-y^2}$ symmetry. The superconducting gap parameter [4] $\Delta_{\vec{k}}$ varies as $\Delta \cos 2\theta$ in the k_x, k_y plane of reciprocal ($\vec{k}$) space, where $\theta = \arctan k_y/k_x$, giving rise to line nodes at 45^o to the x and y symmetry axes, at which the gap goes to zero and the order parameter changes sign. In a seminal paper, Yip and Sauls predicted [5] that there should be a non-linear Meissner effect(NLME) arising from the anomalous back flow of Bogoliubov quasi-particles near these nodes. They showed that at low temperatures (T) the London penetration depth λ should be increased significantly by small applied fields H below the lower critical field H_{c1}, and that there should also be non-linear effects in the transverse magnetisation [5]. The NLME has been studied theoretically by several groups [5–9] who all agree that λ should increase as H^1 at very low temperatures, when the Doppler or energy shift d in the quasiparticle spectrum caused by the flow of supercurrent is larger that k_BT. For $YBa_2Cu_3O_{6+x}$ crystals this condition is only satisfied below approximately 2 K for fields of order $0.5H_{c1}$ or 300 Gauss. At higher temperatures, where $k_BT \gg d$, the theory predicts that the non-linear effect in λ should be much smaller and vary as H^2. In contrast to these predictions, several experimental studies [10–14] show that λ increases as H^1 over most of the temperature range studied (typically 1.4 to 80 K), and that $d\lambda/dH$ becomes larger at higher temperature. Moreover the expected anisotropy in $\delta\lambda(H)$, an increase by a factor $\sqrt{2}$ when H is applied along the nodal directions, and the predicted non-linear transverse magnetic moment have not been observed experimentally [15,16]. One possible explanation for these discrepancies is the occurrence of non-local effects [17] at low T. However in one of the commonly used experimental geometries, where the currents and fields are in the CuO_2 planes, these effects are governed by the c-axis coherence length and would generally be small, although it has been argued [17] that they would still be significant in YBCO.

It is generally agreed that the experiments are difficult and not very reproducible, and it has been suggested that the lack of reproducibility could be caused by trapped flux [13] or the sharp edges of the crystals [15]. My original motivation was to see whether the unusual H^1 dependence of λ mentioned above and perhaps some of the apparent lack of reproducibility could be linked with other physical properties which are extremely dependent on the hole concentration (p). For example the normal state pseudogap develops suddenly when p is less than 0.19 holes per planar Cu atom [18,19], and this could conceivably lead to unusual effects in $\lambda(H)$. The thermoelectric power is often large [20], implying substantial electron-hole asymmetry which might also affect the NLME. However simple model calculations [21] based on standard theory seem to indicate that none of these mechanisms can cause λ to increase linearly with H at higher temperatures.

As discussed in the present paper, a possible explanation of the experimental findings is that Cooper pairs near the nodes of any superconductor with higher order angular momentum pairing are actually broken when the energy difference between the $(\vec{k} + \vec{s}) \uparrow$ and $(-\vec{k} + \vec{s}) \downarrow$ states forming a pair with drift momentum $2\hbar\vec{s}$ exceeds the pair binding energy $2|\Delta_{\vec{k}}|$. An empirical model along these lines gives a reasonably good account of the available experimental data, although further experiments on the same crystal at closely spaced doping levels may be worthwhile. The model gives effects of the same magnitude as Yip and Sauls predicted at low T, but they persist to higher temperatures. It could also be checked experimentally by measuring zinc doped crystals where the

NLME is predicted to be shifted to higher fields because of increased pair-breaking in zero field [22,23]. Extensions of the present approach to higher Doppler shifts (d greater than k_BT) could also be relevant for understanding some properties of cuprate superconductors at higher magnetic fields, for example the penetration depth [24] and the thermal conductivity in the vortex state [25]. However its relation to the usual theory involving the Doppler shift [26,27] needs a more careful study because both pictures predict similar numbers and types of quasiparticles at high fields and the Doppler shift approach does appear to agree with recent thermal conductivity experiments [28].

II. THE EMPIRICAL MODEL

The total supercurrent density $\vec{j}$ in a superconductor is usually expressed as the sum of the contribution $\vec{j}_s$ from Cooper pairs with a drift velocity $\vec{v}_s$ and the contribution from the backflow of quasiparticles $\vec{j}_{qp}$ [7]. For a cylindrical Fermi surface(FS), with quadratic in-plane energy dispersion, and $\vec{v}_s$ in the conducting planes, $\vec{j}_s = ne\vec{v}_s$ where n is the total number of carriers per unit volume. As far as I know, published theoretical treatments of the NLME only consider non-linearity in the quasiparticle term, and implicitly assume that the gap parameter $\Delta_{\vec{k}}$ retains its usual d-wave form. For example [7], for a cylindrical FS, Equations 1 and 2 together with the relation $\vec{j} = \vec{j}_s + \vec{j}_{qp}$, lead to all the non-linear effects proposed until now.

$$j_{qp} = \frac{4en}{mv_F^2}\int_0^\infty \frac{d\epsilon}{2\pi} \times \int_0^{2\pi} d\theta v_F \cos\theta\, f(\sqrt{\epsilon^2 + \Delta^2(\theta)} + mv_F v_s \cos\theta) \quad (1)$$

In this Equation, f is the Fermi function, e the electronic charge, v_F the Fermi velocity, ϵ and m the energy and effective mass of the carriers respectively. The superfluid velocity $\vec{v}_s$ is directed along the crystallographic $\vec{x}$ axis and the angular dependent superconducting energy gap is given by:

$$|\Delta_{\vec{k}}(T)| = \Delta(T,\theta) = \Delta(T)|\cos 2\theta| \quad (2)$$

At low T when the Doppler energy shift of one electron in a Cooper pair, $d = \frac{1}{2}m[(\vec{v}_F + \vec{v}_s)^2 - (\vec{v}_F)^2] = m\vec{v}_F.\vec{v}_s \gg k_BT$, Equations 1 and 2 give the non-analytic variation $\lambda \propto |v_s|$, i.e. $\lambda \propto |H|$ that was predicted by Yip and Sauls [5]. In the opposite limit, $d \ll k_BT$, $\delta\lambda/\lambda$ is expected [7] to vary as H^2/T. Here I suggest that Equation 2 does not hold exactly except when $v_s \to 0$. Namely, as sketched in Figure 1(a), in the parts of the FS where $|d| \geq |\Delta_{\vec{k}}(T)|$, $\Delta(T) = 0$, the Cooper pairs are actually broken and do not contribute to the supercurrent [29]. This differs from the usual picture, shown in Figure 2, where the FS is still displaced near the nodes and the pair current there is completely compensated by the back-flow when (a) $d \gg k_BT$ and $d \geq \Delta(\theta)$, giving strong non-linearity [5] in λ, or (b) $d \ll k_BT$ and $k_BT \gtrsim 3\Delta(\theta)$ and the non-linearity in λ is weak [5]. Pair-breaking is plausible physically because when $|d| \geq |\Delta_{\vec{k}}(T)|$ the energy difference between the two electron states which form a Cooper pair is larger than the pair binding energy, $2|\Delta_{\vec{k}}(T)|$, and in an s-wave superconductor, where $\Delta_{\vec{k}}$ is uniform, this condition corresponds to the critical (depairing) current.

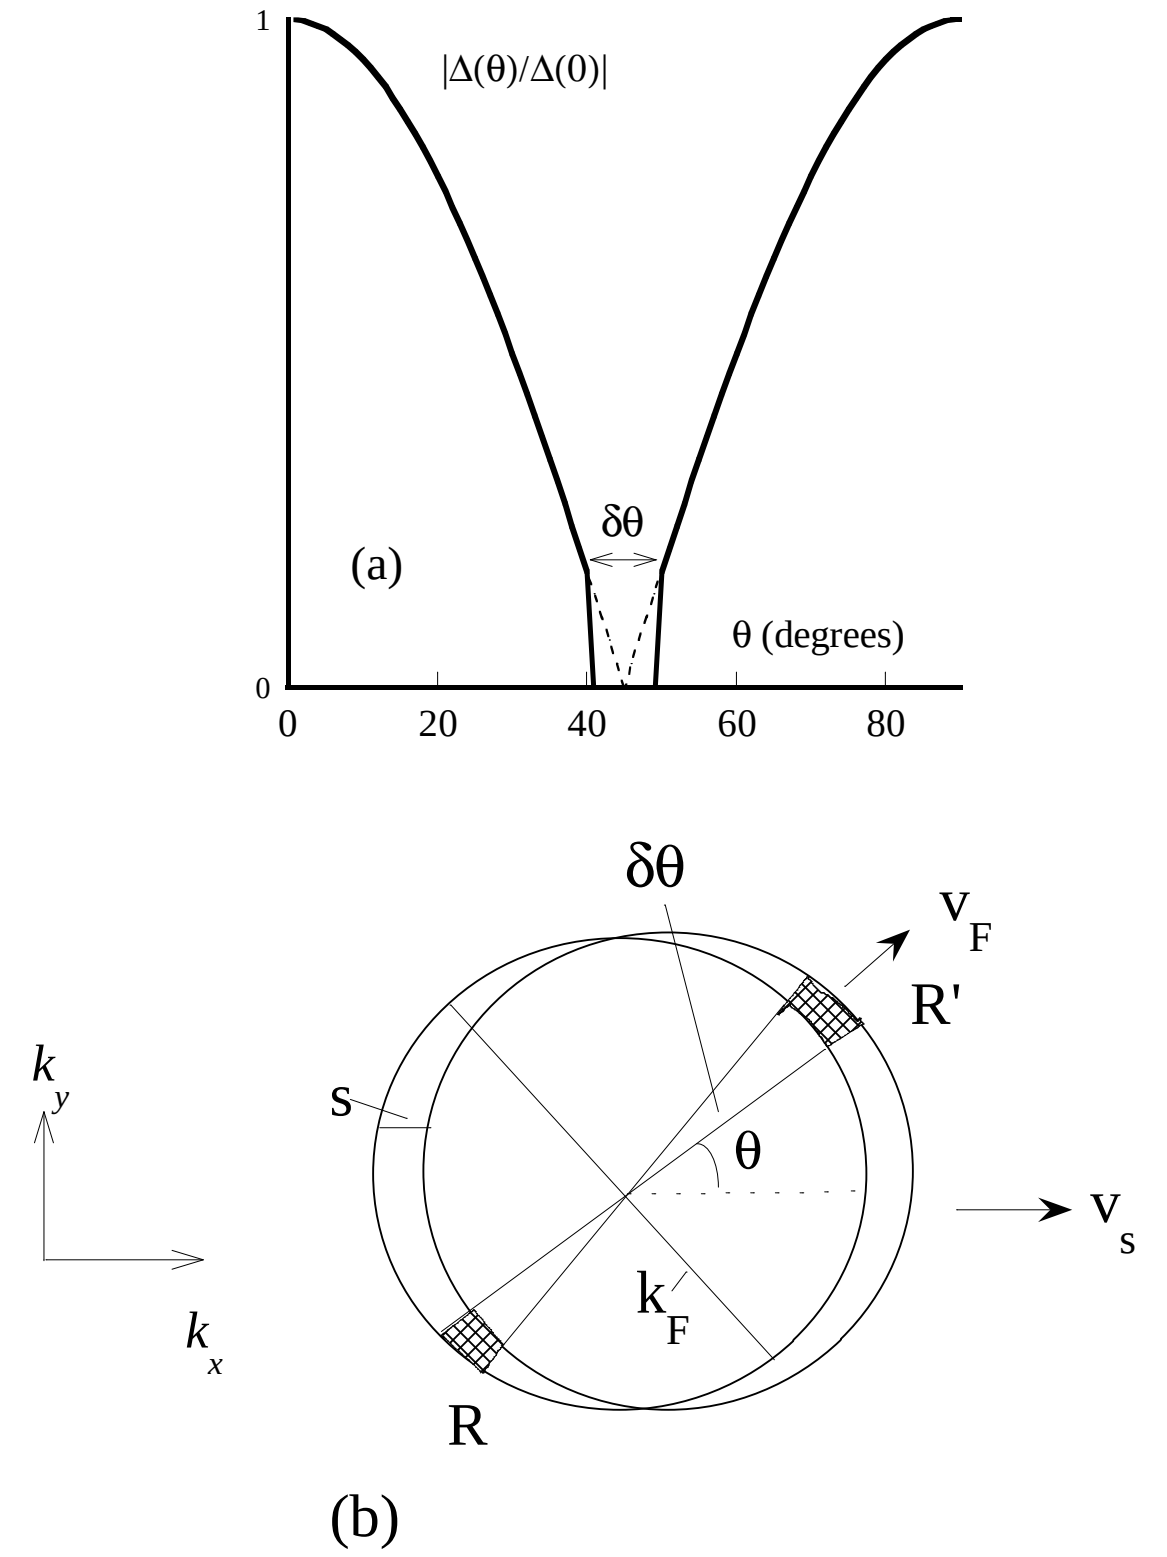

FIG. 1. (a) Suggested angular variation of $|\Delta(\theta)|$ in the presence of a finite supercurrent (solid line). (b) Section of a cylindrical Fermi surface showing the angular regions of width $\delta\theta$ where pairing is suppressed. The loss in current density from Cooper pairs in the angular range $\delta\theta$ is equal to $2ev_F\cos\theta$ (the current change on moving one carrier from R' to R) multiplied by the number of carriers per unit volume in the shaded areas R or R'. See text.

To some extent it can be justified within weak-coupling BCS [30] theory as follows. Using the standard d-wave pairing interaction [31], $V_{kk'} = -Vcos2\theta_k cos2\theta_{k'}$, the BCS Equations [30] 3.15 and 3.16 can be used to compute the increase in free energy F when $\Delta(\theta, T)$ is set equal to zero in a small angular region $\delta\theta$ near the four nodes. For the stationary superfluid this costs an energy:

$$\delta F = \beta\Delta(T,\pi/2)^2\delta\theta^3 N(0) \quad (3)$$

where N(0) is the density of states at the FS for one spin

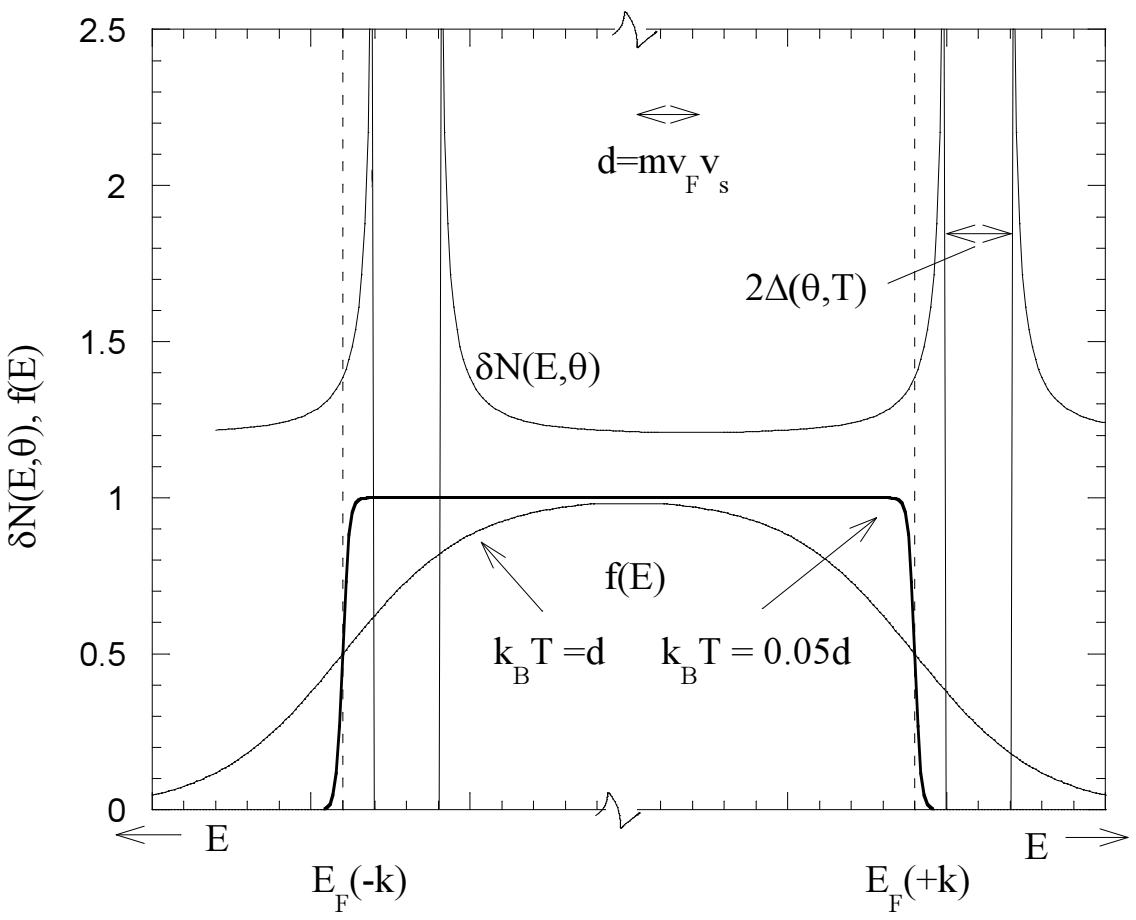

FIG. 2. Partial density of states(DOS) for Doppler shifted Bogoliubov quasi-particles at an angle θ. At low T, e.g. $k_B T = 0.05d$ where d is the Doppler shift, the backflow of quasi-particles in angular regions where the superconducting gap $\Delta(\theta, T) < d$ exactly compensates the flow of Cooper pairs arising from the shifted DOS in those regions [5]. At high T, e.g. $k_B T = d$, this does not happen.

direction, and β is a weakly T dependent constant, which ranges from 1.49 at $T/T_c = 0.16$, to 1.19 at $T/T_c = 0.67$. If only two nodes are affected (e.g. for current flow in the nodal directions) then β is reduced by a factor of two. For the moving superfluid, there are no Cooper pairs in this small angular region, so the kinetic energy K is reduced, and in fact δK varies linearly with $\delta\theta$. However there is also a magnetic self energy term (M) arising from the magnetic field produced by the supercurrents which has the form [4] $\vec{j}.\vec{A}$, where $\vec{A}$ is the magnetic vector potential. In the London gauge [4] $\vec{A} = m\vec{v}_s/e$ and I argue below that $\vec{j}_{qp}$ is not altered by pair-breaking at the nodes. Hence there is a gain in magnetic energy of the form $m\delta\vec{j}_s.\vec{v}_s/e$ arising from the absence of Cooper pairs near the nodes. Referring to Figure 1(b), $\delta\vec{j}_s.\vec{A}$ is given by $2e\vec{v}_F.\vec{A}$, multiplied by the total number of carriers in the region R, namely $s\cos\theta k_F \delta\theta n/\pi k_F^2 = n v_s \delta\theta \cos\theta/\pi v_F$. Hence for one pair of opposite nodes:

$$\delta M = \frac{2}{\pi} n m v_s^2 \delta\theta \cos^2\theta \tag{4}$$

By integrating over the whole of the FS, from $\theta = 0$ to π, it can be seen that $M = nmv_s^2 = 2K$. Minimising the sum of δF and $\delta(M + K)$ with respect to $\delta\theta$ gives:

$$\delta\theta = 0.64 \frac{m v_F v_s}{\Delta(T)} \tag{5}$$

when $\vec{v}_s$ is along a nodal direction. $\delta\theta$ is a factor of $\sqrt{2}$ smaller when $\vec{v}_s \parallel \vec{x}$. This expression has the same form and the same anisotropy as the qualitative argument given above, the presence of the extra factor 0.64 worsens the agreement with experiment slightly and has been omitted in subsequent discussion. This may be an indication that there is another pair-breaking mechanism or another term in the free energy varying linearly with $\delta\theta$, not covered by the above treatment, or that the numbers are changed slightly by strong coupling effects since it is known that for many cuprates $\Delta(0) \approx 3k_B T_c$ rather than the weak coupling d-wave value, $\Delta(0) = 2.14 k_B T_c$.

The effect of the broken pairs on the penetration depth can be estimated in a similar way. A crucial question is whether the carriers produced by the broken pairs will have zero drift velocity in the laboratory frame or whether they will be in equilibrium with the pair current and the Bogoliubov quasiparticles on the remainder of the FS. It seems that only in the latter case will the present model account for the behaviour of λ(H). From Figure 2 it can be seen that in both cases (a) when $k_B T \ll d$ and (b) when $k_B T \gg d$ and $k_B T \gg \Delta(T, \theta)$, the pair supercurrent in that angular region will be balanced by the backflow, to give almost zero net supercurrent, therefore producing stationary carriers by pair-breaking will have almost no effect on λ. This is confirmed by numerical calculations based on Equation 1, namely, if the contributions to j_{qp} and j_s from the angular region $\delta\theta$ are simply omitted there is almost no change in λ for $k_B T \gg d$. On the other hand if the carriers from broken pairs have the same drift velocity as the Bogoliubov quasiparticles then j_{qp} can be calculated from Equation 1, simply by setting $\Delta(\theta) = 0$ near the nodes. For $k_B T \gg d$, δj_{qp} only varies weakly with d, as d^2, while δj_s varies as d^1. Assuming then that the carriers do have the same drift velocity as the Bogoliubov quasiparticles, the loss in supercurrent associated with the broken pairs is given by $\delta j_s = 2nev_s\delta\theta\cos^2\theta/\pi$ for a pair of nodes. This is the same formula used above when calculating the magnetic self energy of the supercurrents. Hence from this formula, $\delta n/n = \delta j_s/j_s = -2\delta\theta/\pi$ for both $\vec{v}_s$ parallel to the nodal directions (2 nodes with $\cos\theta = 1$) and to the anti-nodal directions (4 nodes with $\cos\theta = 1/\sqrt{2}$).

The penetration depth $\lambda(T) = \sqrt{mc^2/4\pi e^2(n - n_{qp})}$, and neglecting non-linear effects on $n_{qp} = |\vec{j_{qp}}/e\vec{v}_s|$ for the reasons given above, this changes by:

$$\frac{\delta\lambda}{\lambda} = -\frac{1}{2}\frac{\delta n}{(n - n_{qp})} \tag{6}$$

Using the relation $H = 4\pi I/c$ between the surface field (H) and the surface current I per unit length yields $H = 4\pi j\lambda/c$, which together with the above expressions for λ and $\delta\theta$ (but omitting the factor of 0.64 in Equation 5) gives:

$$\begin{aligned}\frac{\delta\lambda(H)}{\lambda(T)} &= \frac{\gamma(T)d}{\sqrt{2}\pi\Delta(T)} = \frac{ev_F \mid H \mid \lambda(T)\gamma(T)}{c\sqrt{2}\pi\Delta(T)} \\ &= \frac{\pi \mid H \mid \xi(T)\lambda(T)\gamma(T)}{\sqrt{2}\Phi_0} = \alpha\gamma(T)\frac{\mid H \mid}{H_c(T)}\end{aligned} \tag{7}$$

This expression refers to the case where the current flow is at 45^o to the nodes. According to the present treatment the effect will be a factor of $\sqrt{2}$ larger when the current flows in the nodal directions, as in the work of Yip and Sauls [5]. Φ_0 is the flux quantum for pairs, $\xi(T) = \hbar v_F/\pi\Delta(T)$ is a measure of the in-plane coherence length for a d-wave superconductor and $\gamma(T) \equiv \lambda(T)^2/\lambda(0)^2$. $H_c(T)$ is the thermodynamic critical field, if the standard Ginzburg-Landau expression for an s-wave superconductor, $H_c(T) = \Phi_0/2\sqrt{2}\pi\lambda(T)\xi(T)$ is used, the constant $\alpha = 0.25$. Estimates using parameters for a cylindrical FS give $\alpha = 0.16$ for the weak coupling d-wave case, (for which $\Delta(0) = 2.14k_BT_c$ and $H_c(0)^2/8\pi = 0.125N(0)\Delta(0)^2$) and $\alpha = 0.129$ for the more realistic case $\Delta(0) = 3k_BT_c$ and [33] $H_c(0)^2/8\pi = 0.089N(0)\Delta(0)^2$. Equation 7 has similar form and similar magnitude to the Yip-Sauls result at low T, but it has a different origin, in the present work it arises because the superconducting gap parameter has been suppressed near the nodes, where it no longer obeys Equation 2. The extra factor $\lambda(T)^2/\lambda(0)^2$ results from the assumption that j_{qp}, i.e. n_{qp}, is not changed at all by the presence of pair-breaking. If it were changed in the same ratio as n, i.e. if $\delta n_{qp}/n_{qp} = \delta n/n$, then the $\lambda(T)^2/\lambda(0)^2$ factor would be absent and the temperature dependencies would be in much better agreement with experiment. But there does not seem to be any theoretical justification for such an "ad hoc" hypothesis. The $|H|$ behaviour in Equation 7 will be cut off at low fields by the presence of pair-breaking from other sources, for example at low T from impurities in the CuO$_2$ planes and at higher T by inelastic scattering processes. This effect can be taken into account by replacing $|H|$ by the empirical expression $\sqrt{H^2 + H_0^2} - H_0$, where H_0 is a measure of the pair-breaking effects in the absence of an applied field.

III. COMPARISON WITH EXPERIMENT

Experimental data [15] for the field dependence of λ_a for a detwinned YBa$_2$Cu$_3$O$_{6.95}$ crystal are shown in Figure 3a, together with fits to Equation 7, including the cut-off parameter H_0. The linear terms in these fits correspond to dλ_a/dH values of 0.033 ± 0.001 A^o/Gauss at both 4.2 and 7 K. In contrast to the Yip-Sauls result, the slope calculated from Equation 6 is T-independent at these temperatures. Using the experimental value [15] $\lambda_a(T = 0) = 1600$ Å, leaves one free parameter $\xi_a(0)$ which has to be equal to 16.4 Åto account for the data in Figure 2(a). This value is quite compatible with $\xi_{a-b}(0) = 11$ Åobtained previously by analysing [32] the specific heat above T_c in terms of Gaussian fluctuations bearing in mind that $\xi_{a-b}(0)$ contains a contribution from the Cu-O chains, depends on the FS average of v_F and is related to the RMS average of $\Delta(0)$. Taking $2\Delta(0) = 6k_BT_c$, the value of $\xi_a(0)$ obtained in the present work corresponds to an acceptable value for $v_F = 1.9 \times 10^7$ cm/s in the nodal directions. Using Equation 6 and the same values of $\Delta(0)$ and $\lambda_a(0)$, the value of $H_0 = 30 \pm 10$ Gauss, obtained from the fits, gives a very small pair-breaking energy of 0.5 ± 0.16 K. This compares well with typical values of the pair-breaking temperature $T^* \leq 1$ K obtained from the T dependence of λ in zero field [13,23].

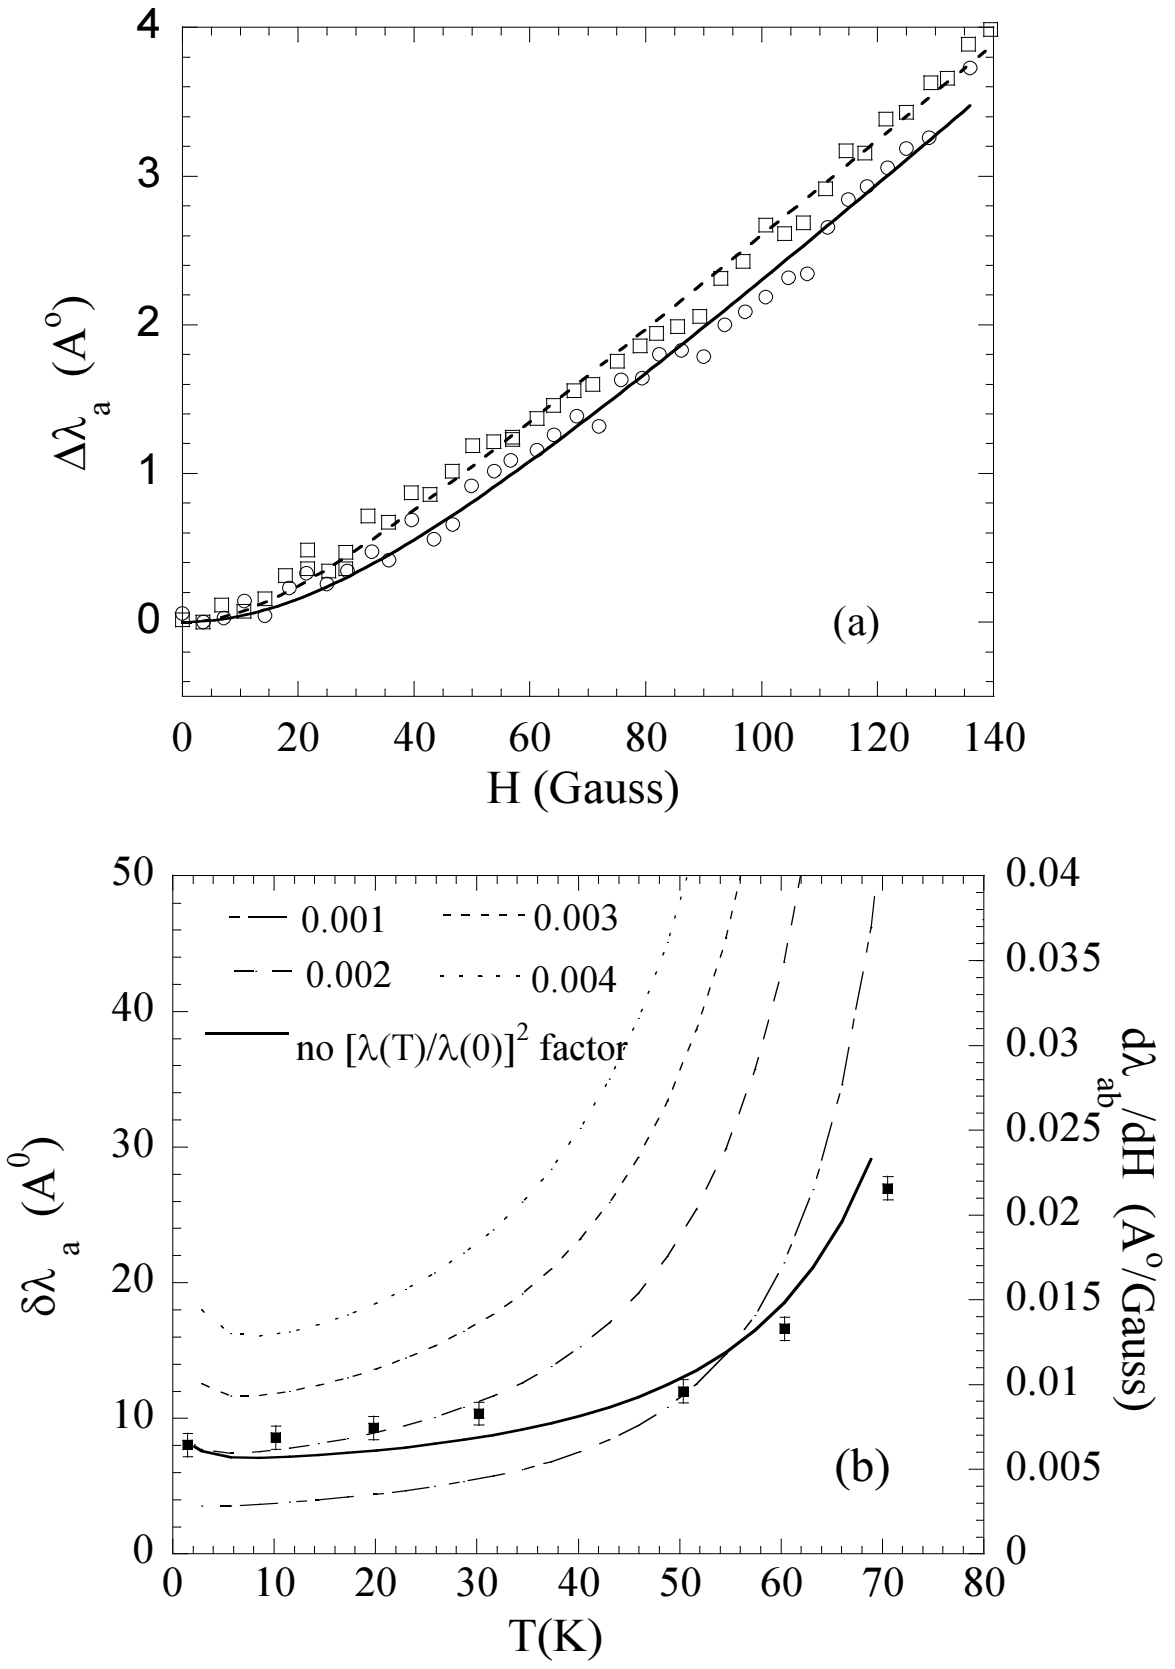

FIG. 3. (a) Field dependence of the a-axis penetration depth of YBa$_2$Cu$_3$O$_{6.95}$ measured [15] for a detwinned crystal at 4.2 K (circles) and 7 K (squares). The dashed and solid lines are fits to the data using Equation 7 together with cut-off fields H_0 of 23 and 42 Gauss respectively. (b) Measured [13] temperature dependence of dλ_{ab}/dH (squares) for a YBa$_2$Cu$_3$O$_{6.95}$ crystal with $T_c = 91.4$ K. The dashed lines show the behaviour calculated according to Equation 7 for various magnetic fields corresponding to $d/\sqrt{2}\Delta(\frac{\pi}{2}, T = 0) = 0.001$ to 0.004. The solid line shows the effect of omitting the $\lambda(T)^2/\lambda(0)^2$ factor, see text.

The measured T dependence [13] of dλ_{ab}/dH is shown in Figure 3b. The fit to Equation 7 using the d-wave behaviour of $\Delta(T)$ and $\lambda(T)$, calculated in the weak-coupling limit for a cylindrical FS, gives the correct general behaviour with some deviations at high T. Exact agreement is not to be expected in view of the fact that the weak-coupling ratio $2\Delta(0) = 4.28k_BT_c$ is smaller than typical experimental values, $2\Delta(0) = 6k_BT_c$. However as also shown in Figure 3b, omission of the $\lambda(T)^2/\lambda(0)^2$ factor gives much better agreement with experiment.

Experimental data for $\delta\lambda_{ab}(H,T)/\lambda_{ab}(0,T)$ versus $H/H_c(T)$ from the work of Maeda and colleagues [10,11]

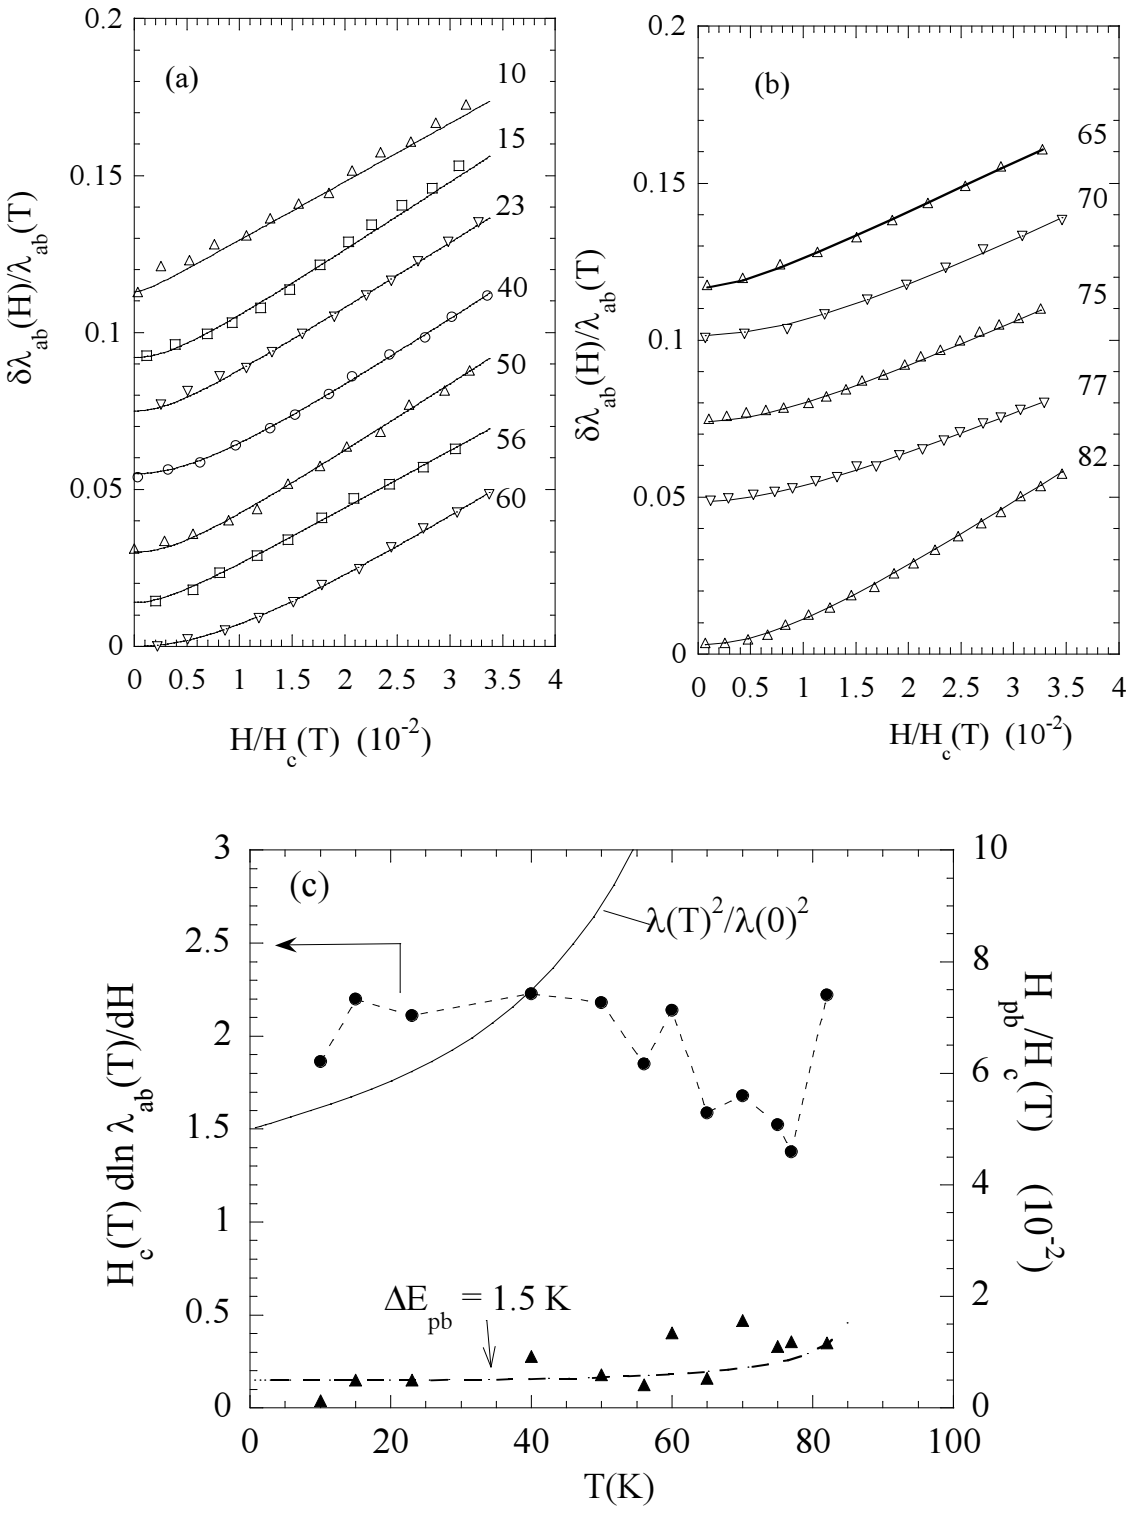

FIG. 4. (a) and (b) Experimental data for the in-plane penetration depth of a Bi:2212 crystal [11] as a function of the applied field, $H \parallel c$, normalised to the thermodynamic critical field $H_c(T)$ at various temperatures. The solid lines show fits to Equation 7. (c) Values of the parameters α(left-hand scale) and $H_0/H_c(T)$ (right- hand scale) determined from these fits, omitting the $\lambda(T)^2/\lambda(0)^2$ factor, which as shown by the solid line gives the wrong T dependence. The dashed line shows the T dependence expected if the pair-breaking parameter H_0 is constant.

for Bi:2212 crystals are shown in Figure 4(a). $H_c(T)$ was derived experimentally [10,11] for the same crystals by assuming that the lowest field H^*, at which some hysteresis could be detected in field sweeps, was a measure of the lower critical field $H_{c1}(T)$. Then $H_c(T)$ was obtained by taking a plausible value $\kappa = 100$ for the Ginzburg-Landau parameter. It can be seen that the data can be fitted to Equation 7 at all reduced temperatures ($t = T/T_c$) studied. However as shown in Figure 4(b) the values of the slopes are essentially constant rather than increasing as $\lambda(T)^2/\lambda(0)^2$ as predicted by Equation 7. Again this extra factor of $\lambda(T)^2/\lambda(0)^2$ is a weak point of the present model. Even without the latter factor the magnitude of the slopes, i.e., α, are about a factor of 10 larger than that calculated above. It was suggested [11] that this was mainly because the effect of the geometrical barrier [34] leads to $H_{c1}(T)$ and hence $H_c(T)$ being overestimated. The crystals used were slightly overdoped with T_c values of 90 K. Although it is known that the condensation energy of Bi:2212 can be reduced by a factor of 2-5 by the presence of the normal state pseudogap [19], even for such high values of T_c, this effect is probably taken into account by using experimentally determined values of $H_c(T)$. The pair-breaking parameter $H_0(T)/H_c(T)$ obtained from these data is also plotted in Figure 4 (b). H_0 is essentially constant in the temperature range studied, showing that inelastic scattering processes are not strong enough to cause pair-breaking.

IV. SUMMARY AND CONCLUSIONS

I have argued that the non-linear Meissner effect in the cuprates can be understood in terms of an empirical model in which the flow of a finite supercurrent destroys superconducting order in a small angular range near the d-wave nodes. This model accounts for some of the experimental data and would mask the unusual temperature dependence predicted by Yip and Sauls. The general viewpoint outlined here is reminiscent of published theoretical work suggesting that application of high fields could actually alter the symmetry of the order parameter, for example by introducing a $d + id$ [35] or a $d + id_{xy}$ component [36]. However for experiments at low fields it seems that the empirical pair-breaking picture described here could be adequate. The present approach, which suggests that the pair-breaking is an intrinsic property, still predicts anisotropic effects for which there is presently no experimental support. Although in this regard one should note that there are potential complications in separating Cu-O$_2$ plane and Cu-O chain contributions to the penetration depth in YBCO and that in the present model the details of any non-linear effects in the magnetisation will be altered by the different behaviour of the free energy. The present work supports the empirical conclusion [10–12] that even though the high temperature NLME is not predicted by the original Yip-Sauls theory, it is nevertheless a characteristic feature of 'non s-wave' superconductivity.

There are indications that measurements of the non-linear Meissner effect as a function of hole concentration could be used as a means of investigating the effect of the normal state gap on the superconducting properties and for investigating pair-breaking mechanisms in zero applied field.

V. ACKNOWLEDGEMENTS

I am grateful to A. Carrington and J.W. Loram for several helpful suggestions and for critically reading the manuscript. Helpful comments from R.W. Giannetta, W.N. Hardy, A. Maeda, K. Maki, D. Scalapino, Tao Xiang and J.R. Waldram are also gratefully acknowledged.

[1] D.J. Van Harlingen, Rev. Mod. Phys. **67**, 515 (1995)

[2] C.C. Tsuei and J.R. Kirtley, Physica C**282-287**, 4 (1997)

[3] C.C. Tsuei and J.R. Kirtley, Phys. Rev. Lett. **85**,182 (2000)

[4] J.R. Waldram, 'Superconductivity of Metals and Cuprates', Institute of Physics Publishing, Bristol and Philadelphia, 1996, Chapter 7.

[5] S.K. Yip and J.A. Sauls, Phys. Rev. Lett. **69**, 2264 (1992)

[6] D. Xu, S.K. Yip and J.A. Sauls, Phys. Rev. B **51**, 16233 (1995)

[7] T. Dahm and D.J. Scalapino, Phys. Rev. B **60**, 13125 (1999)

[8] J.J. Betouras and R. Joynt, Phys. Rev. B **57**, 11752 (1998)

[9] B.P. Stojkovic and O.T. Valls, Phys. Rev. B **51**, 6049 (1995)

[10] A. Maeda, Y. Iino, T. Hanaguri, N. Motohira, K. Kishio and T. Fukase, Phys. Rev. Lett. **74**, 1202 (1995)

[11] A. Maeda et al., Journ. Phys. Soc. Japan, **65**,3638 (1996)

[12] A. Maeda, H. Yasuda and T. Hanaguri, Journ. Phys. Soc. Japan, **68**,594 (1999)

[13] A. Carrington, R.W. Giannetta, J.T. Kim and J. Giapintzakis, Phys. Rev. B **59**, R14173 (1999)

[14] C.P. Bidinosti, W.N. Hardy, D.A. Bonn and R. Liang, preprint, cond-mat/9808231

[15] C.P. Bidinosti, W.N. Hardy, D.A. Bonn and R. Liang, Phys. Rev. Lett. **83**, 3277 (1999)

[16] A. Bhattacharya, I. Zutic, O.T. Valls, U. Welp and B. Veal, Phys. Rev. Lett. **82**, 3132 (1999)

[17] M.-R. Li, P.J. Hirschfeld and P. Wolfe, Phys. Rev. Lett. **81**, 5640 (1998)

[18] J.W. Loram, K.A. Mirza, J.R. Cooper, W.Y. Liang and J.M. Wade, Journ. of Superconductivity, **7**, 243 (1994)

[19] J.W. Loram, J.L. Luo, J.R. Cooper, W.Y. Liang and J.L. Tallon, Procs. of M^{2}S-HTSC-VI Conference, Houston, Texas, Feb. 20-25th, 2000, to appear in Physica C

[20] S.D. Obertelli, J.R. Cooper and J.L. Tallon, Phys. Rev. B **46**, 14928 (1992)

[21] J.R. Cooper (unpublished)

[22] J.W. Loram, K.A. Mirza and P.A. Freeman, Physica C**171**, 243 (1990)

[23] D.A. Bonn, S. Kamal, K. Zhang, R. liang, D.J. Baar, E. Klein and W.N. Hardy, Phys. Rev. B **50**, 4051 (1994)

[24] J.E. Sonier et al., Phys. Rev. Lett. **83**, 4156 (1999)

[25] H. Aubin, K. Behnia, M. Ribault, R. Gagnon and L. Taillefer, Phys. Rev. Lett. **78**, 2624 (1997)

[26] G.E. Volovik, JETP Lett. **58**,469 (1993)

[27] C. Kubert and P.J. Hirschfeld, Phys. Rev. Lett. **80**, 4963 (1998)

[28] M. Chiao, R.W. Hill, C. Lupien, B. Popic, R. Gagnon and L. Taillefer, Phys. Rev. Lett. **82**, 2943 (1999)

[29] It may be helpful to remind the reader that in BCS theory, pairs with arbitrary small values of $\Delta_{\vec{k}}$ still contribute to the pair supercurrent because the magnitudes of the coefficients $u_{\vec{k}}$ and $v_{\vec{k}}$ in the BCS wave-function are always $1/\sqrt{2}$ for $|\vec{k}| = k_F$, but if $|\Delta_{\vec{k}}| \ll k_BT$ this will be completely compensated by the back-flow of Bogoliubov quasi-particles. In this paper the term pair-breaking or broken pairs means that both $u_{\vec{k}}$ and $v_{\vec{k}}$ are zero in a finite angular region near the nodes.

[30] J. Bardeen, L.N. Cooper and J.R. Schrieffer, Phys. Rev. **108**, 1175 (1957)

[31] K. Maki and H. Won, J. Phys. France **6**, 2317 (1996)

[32] J.W. Loram, J.R. Cooper, J.M. Wheatley, K.A. Mirza and R.S. Liu, Phil. Mag. B **65**, 1405 (1992)

[33] J.W. Loram (unpublished)

[34] E. Zeldov, A.I. Larkin, V.B. Geshkenbein, M. Konczykowski, D. Majer, B. Khaykovich, V.M. Vinokur and H. Shtrikman, Phys. Rev. Lett. **73**, 1428 (1994)

[35] A.V. Balatsky, Phys. Rev. B **61**, 6940 (2000)

[36] R.B. Laughlin, Phys. Rev. Lett. **80**, 5188 (1998)